

Dec. 4 2002: Lecture 29:

Important Geometrical Constructions

Last Time

Graphical Construction for Extracting Chemical Potentials of Solution

The Common Tangent Construction



The equilibrium condition, that the chemical potentials of components must have equal values in all phases, indicates that at equilibrium compositions that have the same tangent (*i.e.*, a *common tangent*).

This result allows equilibrium to be determined by a geometrical construction: the common tangent construction.

Consider the region of lines that lies inside the common tangent point in Figure 28-5, a mixture of $f^{\text{liquid}} G^{\text{sol liquid}}(X_L, T, P) + f^{\text{solid}} G^{\text{sol solid}}(X_S, T, P)$ has lowest value of \bar{G} where f^{liquid} is the fraction of the system that is liquid and f^{solid} fraction of system that is solid.

$$f^{\text{solid}} + f^{\text{liquid}} = 1$$

This corresponds to a diagram that maps stable compositions of phase mixtures:

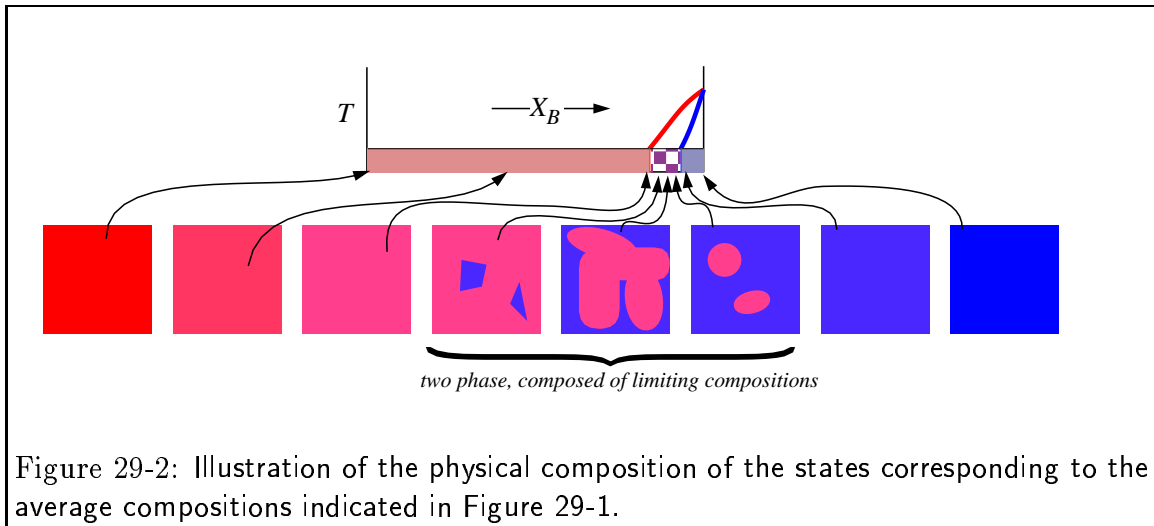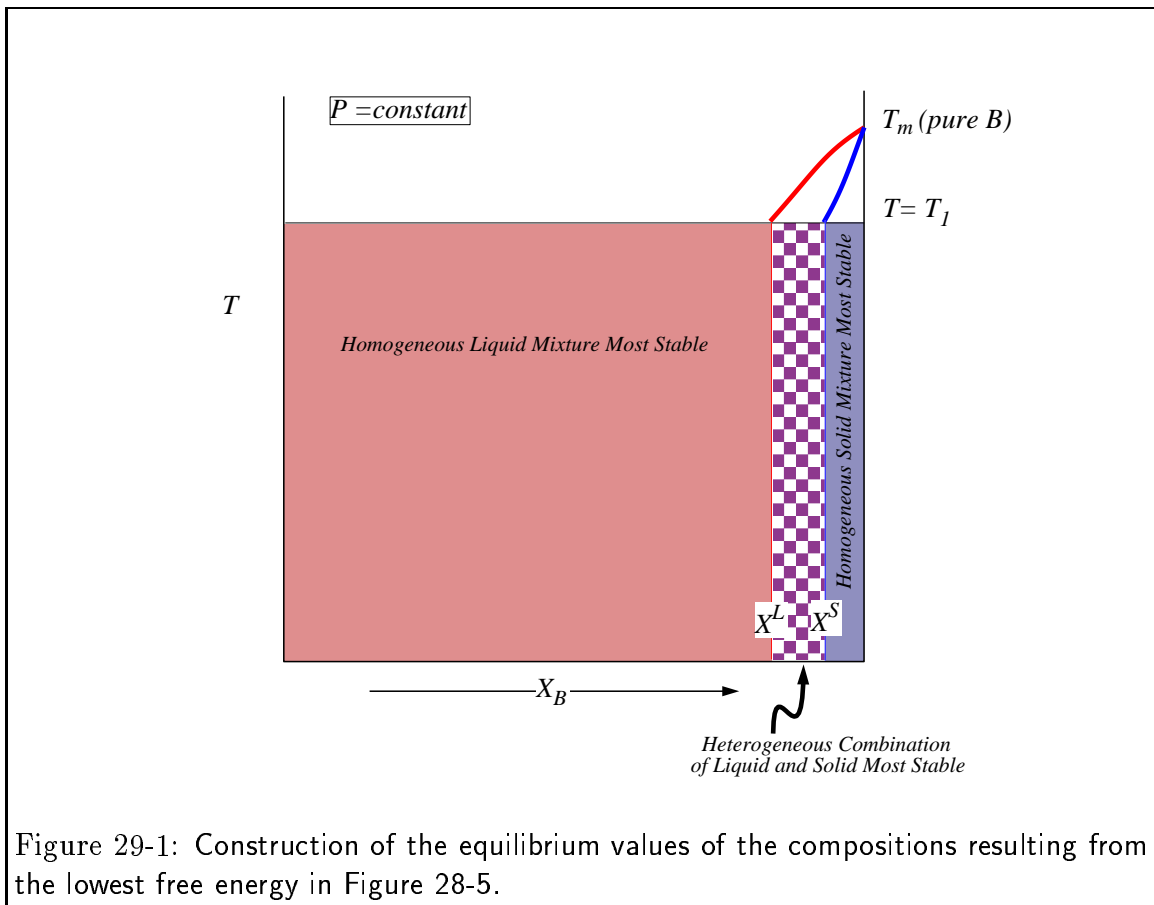


There is a range of “average compositions” at $T < T_M^B$ in which the system has as its most stable form a mixture of liquid at composition X_L and solid at composition X_S . The fractions of f^{liquid} and f^{solid} come from the requirements that the average composition is given by:

$$\begin{aligned} \langle X \rangle &= X^{\text{liquid}} f^{\text{liquid}} + X^{\text{solid}} f^{\text{solid}} \\ &= X^{\text{liquid}} f^{\text{liquid}} + X^{\text{solid}} (1 - f^{\text{liquid}}) \end{aligned} \quad (29-1)$$

or, for the general case where the two phases in equilibrium are α and β :

$$f^\alpha = \frac{X^\beta - \langle X \rangle}{X^\beta - X^\alpha} \quad \text{and} \quad f^\beta = \frac{\langle X \rangle - X^\alpha}{X^\beta - X^\alpha} \quad (29-2)$$

Equation 29-2 is called the lever rule:

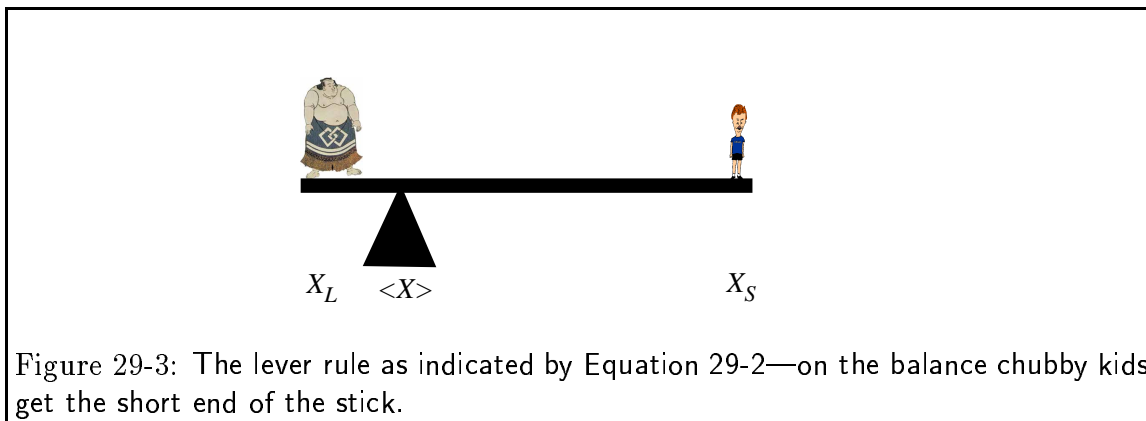

A Menagerie of Pure Component Phase Diagrams

The graphics in this section were created by Angela Tong, MIT.

